arXiv:1111.5762v1 [cond-mat.mtrl-sci] 24 Nov 2011

On Oxygen Non-Stoichiometry in Layered Sodium Cobaltate $Na_xCoO_{2-\delta}$

Simone Casolo[a*] and Ole Martin Løvvik[b,c]
[a] *Dipartimento di Chimica Fisica ed Elettrochimica,*
Universitá degli Studi di Milano,
via Golgi 19, 20133 Milan, Italy.
[b] *Department of Physics, University of Oslo,*
P.O. Box 1048 Blindern, NO-0316 Oslo, Norway
[c] *SINTEF, Materials and Chemistry,*
Forskningsvn. NO-0314 Oslo, Norway

Sodium cobaltate at high Na content is a promising thermoelectric material. It has been recently shown that oxygen vacancies can alter the material properties, reducing its figure of merit. However, experimental data about the oxygen stoichiometry are contradictory. We therefore studied the formation of oxygen vacancies in Na_xCoO_2 with first principles calculations, focusing on x=0.75. We show that a very low oxygen vacancy concentration is expected at the temperatures and partial pressures relevant for applications.

In recent years layered sodium cobaltate, Na_xCoO_2, has attracted much attention because of its remarkable electronic and magnetic properties. Most of the interesting physics of this material comes from its quasi-2 dimensional cobalt oxide layers, surrounded by intercalating Na ions[1–3]. By changing the sodium content, one can continuously tune the oxidation state of the cobalt ions. At high Na content, the majority of Co ions are in a 3+ oxidation state, and charge carriers are diluted holes. In this regime, the thermopower is particularly high probably due to the hole hopping mechanism occurring from Co^{4+} to Co^{3+} along the oxide planes [4, 5].

The influence of point defects other than Na vacancies on sodium cobaltate is still debated. It has been recently reported that oxygen vacancies could have an interesting two-fold effect on the thermoelectric properties. Firstly, they can affect the cobalt oxidation state, *i.e.* reducing charge carrier concentration and increasing the thermopower. Unfortunately, such defects also lower the phonon scattering so that the overall effect is a reduction of the figure of merit of $Na_xCoO_{2-\delta}$ with increasing the defects concentration (δ) [6].

Experimental data about the concentration of vacancies in sodium cobaltate are contradictory, especially at $x \sim 0.75$. While some groups have identified an oxygen non-stoichiometry up to $\delta = 0.16$ [6–9], others found no vacancies within the experimental error [10, 11]. In order to clarify this, we have in this work studied the oxygen vacancy formation in $Na_{0.75}CoO_2$ by first principles density functional theory (DFT) calculations, at various temperatures and oxygen partial pressures. We found that oxygen vacancies have high free energies of formation even at high T, suggesting that the experimentally observed weight loss may have a different origin.

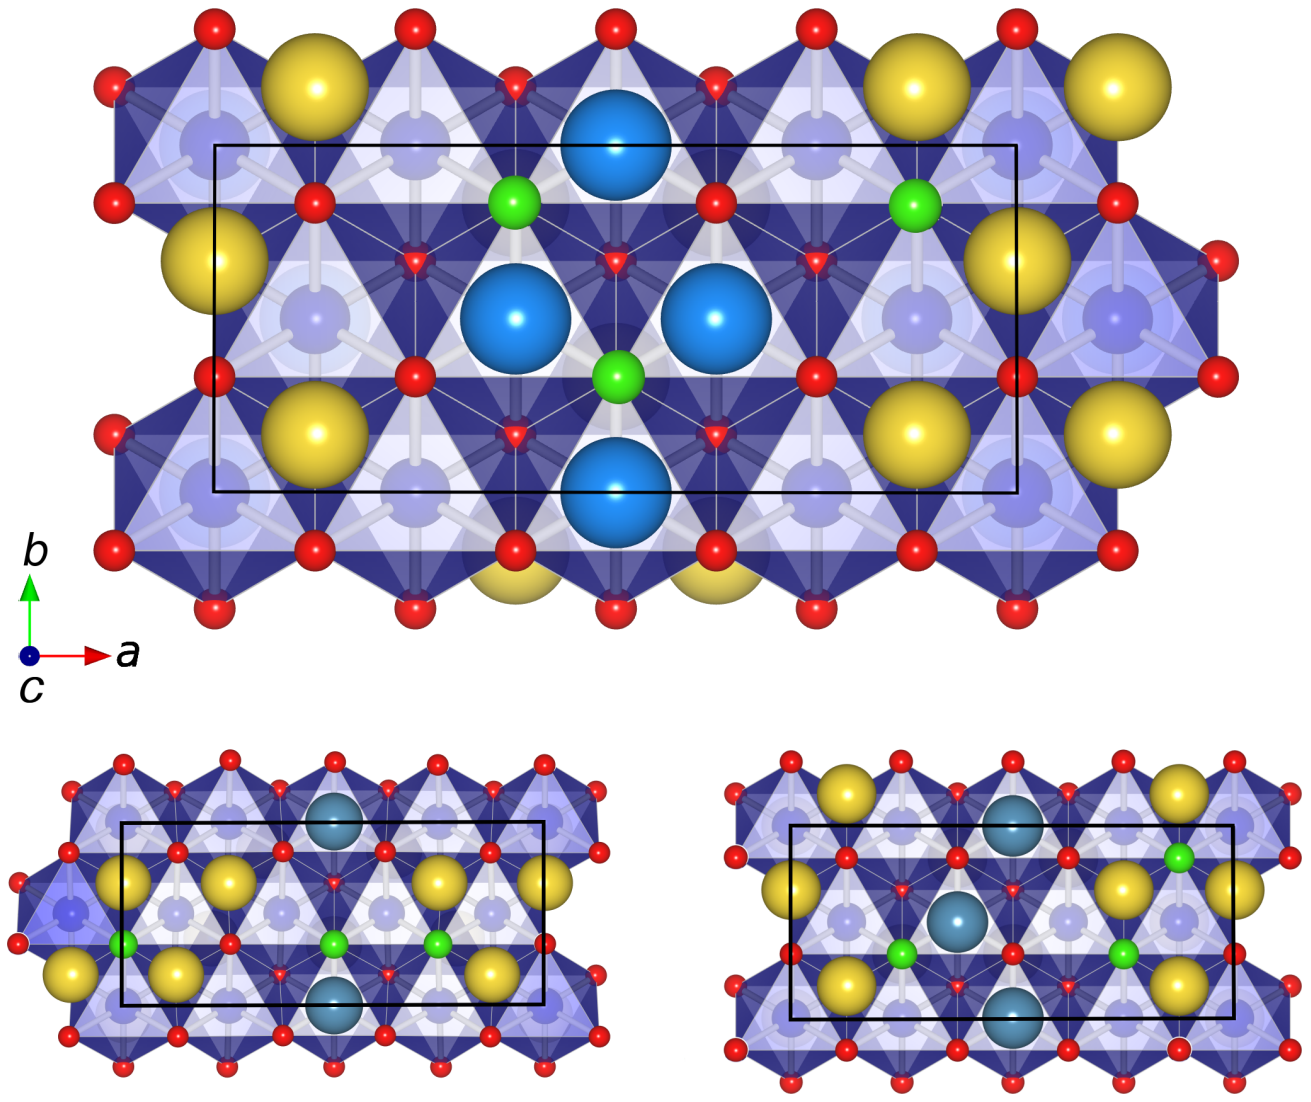

Figure 1: Structure of the three $Na_{0.75}CoO_2$ models, in their starting (non relaxed) positions, as looking along the $00\bar{1}$ direction. Top panel: Diamond, Bottom left panel: FHC, Bottom right panel: ZigZag model. Na1 sites are shown as light blue balls, and Na2 as yellow balls. Co ions are shown as dark balls at the center of the blue CoO_6 octahedra. All the oxygen sites are shown in red, but the ones removed in the vacancy calculations, shown in green.

We assumed the following reaction (using Kröger-Vink notation):

$$Na_xCoO_2 \rightleftharpoons Na_xCoO_{2-\delta} + \delta V_O^{q\bullet} + q\delta e' + \frac{\delta}{2}O_2 \qquad (1)$$

The Gibb's free energies of formation for oxygen vacancies $\Delta G_f(P,T)$ at a pressure P and temperature T were accordingly computed from

$$\Delta G_f(P,T) = G_{def}(P,T) - G_{perf}(P,T) + \frac{1}{2}\mu_{O_2}(P,T) + q\mu_e \qquad (2)$$

where q is the charge state per defect, and μ_i is the chemical potential of the species i. Thermal contribu-

---

[*] Electronic address: simone.casolo@unimi.it

tions of the solid were considered as negligible with respect to those of the oxygen gas, whose chemical potential $\mu_{O_2}(P,T)$ was calculated from

$$\mu_{O_2}(P,T) = H_{O_2}(P^0,0)+\Delta\mu_{O_2}(P^0,T)+k_BT\ln\left(\frac{P}{P^0}\right), \quad (3)$$

where k_B is the Boltzmann constant. The dependence of μ_{O_2} on the temperature $\Delta\mu_{O_2}$ was taken from thermodynamic tables, while enthalpies at $T = 0$ K and standard pressure were taken as the calculated DFT total electronic energies. System charge q was simulated by adjusting the total number of electrons in the cell and at the same time adding a compensating jellium background to avoid diverging Coulomb contributions. The electron chemical potential was determined by the Fermi energy corrected to account for the charge adjustment[12].

Periodic DFT as implemented in the VASP package [13] was used throughout this work. A spin polarized gradient corrected Perdew-Burke-Ernzerhof (PBE) functional [14] was used with a plane wave energy cutoff of 600 eV. Core electrons were included through the projector augmented wave (PAW) method [15]. The reciprocal space was sampled by a Γ-centered **k**-point grid in which the maximum distance between points is 0.15 $\times 2\pi/|a|$. Ionic positions were relaxed until the maximum force was lower than 0.03 eVÅ^{-1}. Simultaneous relaxation of the lattice parameters was performed for the defect free structures.

To sample the many possible sodium ordered structures we adopted three different models for $Na_{0.75}CoO_2$. They are shown in Fig. 1 and named *diamond, filled honeycomb (FHC)* and *zigzag*. They are based on a tetragonal $\sqrt{3}\times 4\times 1$ supercell consisting of 16 formula units [16] and they represent different occupation ratios (1, 1/2, and 1/5) of the two Na crystallographic inequivalent sites: Na1 and Na2. The three models are based on the experimental structure reported by Zandbergen *et al.*[2] (Diamond), and on the theoretical study of Meng *et al.*[3, 17] (FHC and ZigZag). These were chosen as a representative selection of simple periodic models from the large manifold of structures, suitable for a first principles study. Nevertheless, Na self-diffusion is an efficient process already at room temperature [18], so we expect a strong Na disorder at high T.

We considered oxygen vacancies at three different positions for each of the three models, shown as green balls in Fig. 1. We first note that the models with oxygen vacancies are half-metallic (not shown here), similarly to the stoichiometric $Na_{0.75}CoO_2$ structure. Oxygen vacancies were considered in their neutral, +1 and +2 oxidation states, hence as $V_O^{\times}$, $V_O^{\bullet}$ and $V_O^{\bullet\bullet}$, and their free energies of formation (ΔG_f) are shown in Table 1 for the high temperature regime ($T = 1000$ K) relevant for applications. Results are reported for the three different models in both a $\sqrt{3}\times 4\times 1$ and $\sqrt{3}\times 8\times 1$ supercell, corresponding to $Na_{0.75}CoO_{2-\delta}$ with $\delta = 0.031$ and $\delta = 0.016$, respectively. The table values were based on the Fermi energy E_F of the perfect material and $P(O_2) = 1.0$ atm.

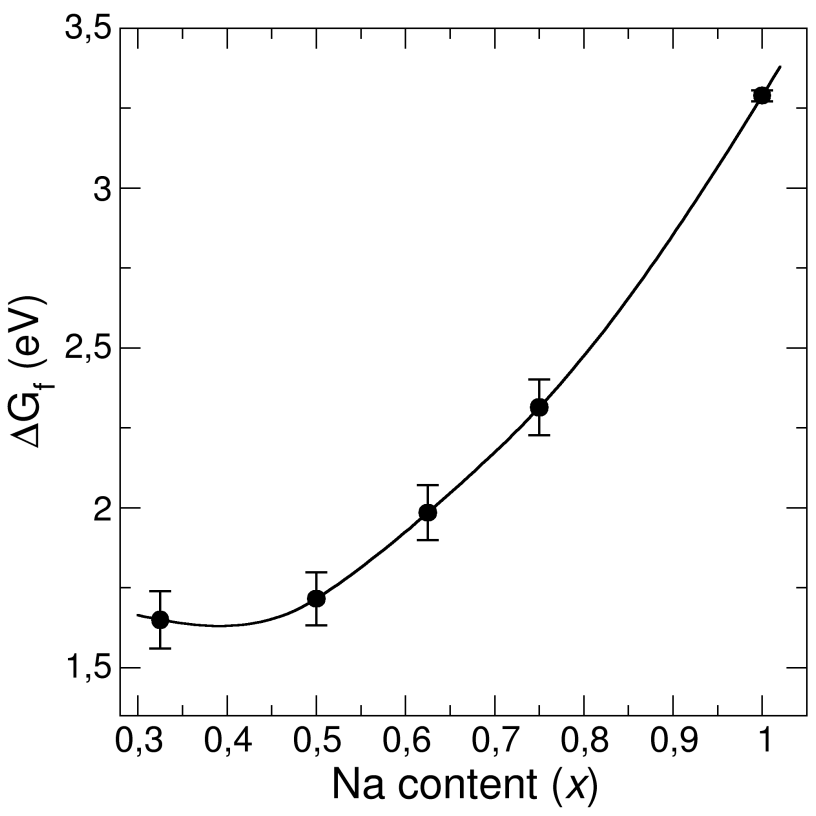

Figure 2: Formation energy for the doubly charged oxygen vacancy as a function of the Na content. Each formation energy has been calculated from a few structures with different ordering, mean values and standard deviations are shown. Line is a guidance for the eye. See text for details.

	ΔG_f (eV)					
	δ=0.031			δ=0.016		
	$V_O^{\bullet\bullet}$	$V_O^{\bullet}$	$V_O^{\times}$	$V_O^{\bullet\bullet}$	$V_O^{\bullet}$	$V_O^{\times}$
Diam1	2.19	2.26	2.30	2.27	2.27	2.28
Diam2	2.30	2.32	2.35	2.32	2.34	2.36
Diam3	2.29	2.33	2.36	2.35	2.37	2.39
ZigZag1	2.35	2.37	2.37	2.36	2.37	2.39
ZigZag2	2.32	2.37	2.39	2.39	2.40	2.40
ZigZag3	2.37	2.42	2.44	2.41	2.43	2.45
FHC1	2.46	2.44	2.48	2.40	2.39	2.42
FHC2	2.37	2.39	2.41	2.38	2.37	2.39
FHC3	2.19	2.24	2.26	2.20	2.23	2.25

Table I: Defect formation free energy as defined in Eq. 2 for neutral, singly and doubly charged oxygen vacancy in $Na_{0.75}CoO_{2-\delta}$ computed for two different δ values. $T = 1000$ K and $P(O_2) = 1.0$ atm. All the values are in eV.

Formation energies are distributed in a narrow range of 0.2 eV, with no clear preference for any of the structural models. This suggest that the Na ordering only plays a minor role for the vacancy formation energy. The distribution of formation energies is also narrow for the two vacancy concentrations δ; lower than 0.1 eV in most of the cases. This means that the Coulomb potential generated by the charged defect is efficiently screened already at the length scale of the shortest lattice parameter, *i.e.* ∼5.0 Å. Nevertheless, it appears that the doubly charged defect $V_O^{\bullet\bullet}$ is slightly favored compared to the other two possible charges, suggesting

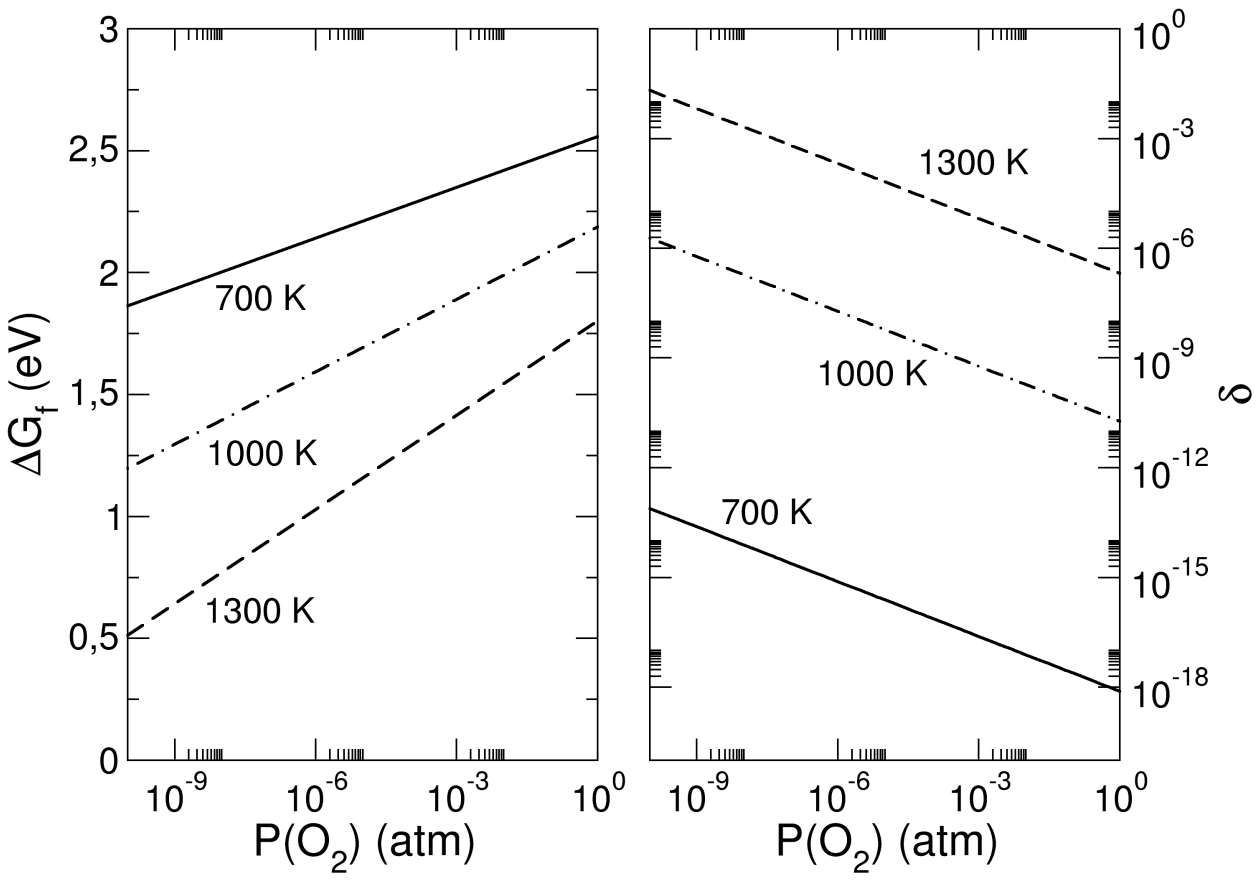

Figure 3: Formation free energy (left) and concentration (right) of doubly charged oxygen vacancies as a function of oxygen partial pressure. Three different temperatures are investigated.

a non-perfect dielectric screening (Fermi liquid).

Overall, the defect formation energies shown in Table 1 are quite high, ranging from 2.19 to 2.48 eV at $T = 1000$ K and $P(O_2) = 1.0$ atm, implying a very low concentration of vacancies. Since the Na ions are very mobile at high temperature, one could expect large local variations of the sodium concentration, modifying the local vacancy formation energies. We therefore studied the $V_O^{\bullet\bullet}$ defect formation for a range of Na concentrations x. Two structures were generated for each x value, and the oxygen vacancy was created at three different sites for each Na arrangement. Averaged results are shown in Fig.2, using the same conditions as in Table 1. When the Na content is reduced, ΔG_f lowers almost linearly down to x=0.50, where it reaches a plateau of about 1.70 eV. The change in the formation energies is substantial, but in $Na_{0.75}CoO_2$ it is unlikely that diffusion alone could create (even locally) low enough Na concentrations to reduce ΔG_f by *e.g.* 1 eV.

In order to quantify the vacancies concentration under experimental conditions we calculated ΔG_f for $x = 0.75$ at different temperatures for the structure with lowest free energy of formation (2.18 eV) in Table 1. The results are shown in the left panel of Figure 3 for three different temperatures (700, 1000 and 1300 K) as a function of $P(O_2)$. In the right panel we show the corresponding vacancy concentration per formula unit, δ. We also note that our formation energies are in good agreement with those recently reported by Yoshiya *et al.* [19] for $x = 0.50$ and $x = 1$. It is clear that the oxygen vacancy free energy of formation is very high at relevant temperatures and oxygen partial pressures. This conclusion holds also when taking into account errors arising from the methodology or approximations we adopted. Even at extreme experimental conditions such as $T = 1300$ K (close to the homogeneous melting point[20]) and $P(O_2) = 10^{-7}$ atm the vacancy concentration would be as little as $\delta \simeq 6.5 \times 10^{-4}$. If more common experimental conditions are chosen, *e.g.* $T = 700$ K and $P(O_2) = 10^{-1}$ atm, we obtain $\delta \sim 10^{-18}$. This is several orders of magnitude lower than reported in some previous publications, *e.g.* Ref. [6].

Our results may help to settle the disagreement between experimental reports on the oxygen stoichiometry in Na_xCoO_2. At high sodium content, concentrations of vacancies ranging from $\delta = 0.05$ to 0.16 have been reported[6, 8, 9], but other studies have concluded that the oxygen concentration is indeed stoichiometric[10, 11]. Our results are clearly consistent with the latter ones.

We can here only speculate on the reason for this discrepancy. One possible explanation is existence of secondary phases in some of the experiments, where these phases are responsible for the oxygen weight loss upon reduction of oxygen partial pressure. Other possibilities comprise Na evaporation, the presence of other defects than considered here, or unintended interaction between the sample and experimental setup.

In conclusion, we showed that the equilibrium concentration of oxygen vacancies in sodium cobaltate is very low at conditions relevant for applications as thermoelectric material, solving a long lasting experimental controversy.

We acknowledge Truls Norby, Harald Fjeld and Tor Svendsen Bjørheim for helpful suggestions, the Research Council of Norway through the Renergi program for economic support, and the NOTUR consortium for providing access to their computational facilities.

---

[1] Y. Hinuma, Y. S. Meng, and G. Ceder, Phys. Rev. B **77**, 224111 (2008).

[2] H. W. Zandbergen, M. Foo, Q. Xu, V. Kumar, and R. J. Cava, Phys. Rev. B **70**, 024101 (2004).

[3] Y. S. Meng, Y. Hinuma, and G. Ceder, J. Chem. Phys. **128**, 104708 (2008).

[4] M. Lee, L. Viciu, L. Li, Y. wang, M. L. Foo, S. Watauchi, R. A. Pascal, R. J. Cava, and N. P. Ong, Nature Mater. **5**, 573 (2006).

[5] Y. Wang, N. S. Rogado, R. J. Cava, and N. P. Ong, Nature **423**, 425 (2003).

[6] P. H. Tsai, T. Norby, T. T. Tan, R. Donelson, Z. D. Chen, and S. Li, Appl. Phys. Lett. **96**, 141905 (2010).

[7] A. Stokłosa, J. Molenda, and D. Than, Solid State Ionics **15**, 211 (1985).

[8] M. Bañobre-Lopez, F. Rivadulla, R. Caudillo, M. A. lopez-Quintela, J. Rivas, and J. B. Goodenough, Chem. Mater. **17**, 1965 (2005).

[9] F. C. Chou, E. T. Abel, J. H. Cho, and Y. S. Lee, J. Phys. Chem. Solids **66**, 155 (2005).

[10] L. Viciu, Q. Huang, and R. J. Cava, Phys. Rev. B **73**, 212107 (2006).

[11] J. Choi and A. Manthiram, Phys. Rev. B **74**, 205114 (2006).

[12] T. Mattila and A. Zunger, Phys. Rev. B **58**, 1367 (1998).

[13] G. Kresse and J. Hafner, Phys. Rev. B **49**, 14251 (1994).

[14] J. P. Perdew, K. Burke, and M. Ernzerhof, Phys. Rev. Lett. **77**, 3865 (1996).

[15] P. E. Blöchl, Phys. Rev. B **50**, 17953 (1994).

[16] R. J. Balsys and R. L. Davis, Solid State Ionics **93**, 279 (1996).

[17] Y. S. Meng, A. van der Ven, M. K. Y. Chan, and G. Ceder, Phys. Rev. B **72**, 172103 (2005).

[18] M. Weller, A. Sacchetti, H. R. Ott, K. Mattenberger, and B. Batlogg, Phys. Rev. Lett. **102**, 056401 (2009).

[19] M. Yoshiya, T. Okabayashi, M. Tada, and C. A. J. Fisher, J. Elect. Mater. **39**, 1681 (2010).

[20] J. B. Peng and C. T. Lin, J. Cryst. Growth **311**, 921 (2009).